

ISSN 2518-1467 (Online),
ISSN 1991-3494 (Print)

ҚАЗАҚСТАН РЕСПУБЛИКАСЫ
ҰЛТТЫҚ ҒЫЛЫМ АКАДЕМИЯСЫНЫҢ

Х А Б А Р Ш Ы С Ы

ВЕСТНИК

НАЦИОНАЛЬНОЙ АКАДЕМИИ НАУК
РЕСПУБЛИКИ КАЗАХСТАН

THE BULLETIN

THE NATIONAL ACADEMY OF SCIENCES
OF THE REPUBLIC OF KAZAKHSTAN

PUBLISHED SINCE 1944

5

SEPTEMBER – OCTOBER 2020

ALMATY, NAS RK

NAS RK is pleased to announce that Bulletin of NAS RK scientific journal has been accepted for indexing in the Emerging Sources Citation Index, a new edition of Web of Science. Content in this index is under consideration by Clarivate Analytics to be accepted in the Science Citation Index Expanded, the Social Sciences Citation Index, and the Arts & Humanities Citation Index. The quality and depth of content Web of Science offers to researchers, authors, publishers, and institutions sets it apart from other research databases. The inclusion of Bulletin of NAS RK in the Emerging Sources Citation Index demonstrates our dedication to providing the most relevant and influential multidiscipline content to our community.

Қазақстан Республикасы Ұлттық ғылым академиясы "ҚР ҰҒА Хабаршысы" ғылыми журналының Web of Science-тің жаңаланған нұсқасы Emerging Sources Citation Index-те индекстелуге қабылданғанын хабарлайды. Бұл индекстелу барысында Clarivate Analytics компаниясы журналды одан әрі the Science Citation Index Expanded, the Social Sciences Citation Index және the Arts & Humanities Citation Index-ке қабылдау мәселесін қарастыруда. Web of Science зерттеушілер, авторлар, баспашылар мен мекемелерге контент тереңдігі мен сапасын ұсынады. ҚР ҰҒА Хабаршысының Emerging Sources Citation Index-ке енуі біздің қоғамдастық үшін ең өзекті және беделді мультидисциплинарлы контентке адалдығымызды білдіреді.

НАН РК сообщает, что научный журнал «Вестник НАН РК» был принят для индексирования в Emerging Sources Citation Index, обновленной версии Web of Science. Содержание в этом индексировании находится в стадии рассмотрения компанией Clarivate Analytics для дальнейшего принятия журнала в the Science Citation Index Expanded, the Social Sciences Citation Index и the Arts & Humanities Citation Index. Web of Science предлагает качество и глубину контента для исследователей, авторов, издателей и учреждений. Включение Вестника НАН РК в Emerging Sources Citation Index демонстрирует нашу приверженность к наиболее актуальному и влиятельному мультидисциплинарному контенту для нашего сообщества.

Б а с р е д а к т о р ы

х.ғ.д., проф., ҚР ҰҒА академигі

М.Ж. Жұрынов

Р е д а к ц и я а л қ а с ы:

Абиев Р.Ш. проф. (Ресей)
Абылкасымова А.Е. проф., академик (Қазақстан)
Аврамов К.В. проф. (Украина)
Аппель Юрген проф. (Германия)
Баймұқанов Д.А. проф., академик (Қазақстан)
Баймұратов У.Б. проф., академик (Қазақстан)
Байтанаев Б.А. проф., академик (Қазақстан)
Байтулин И.О. проф., академик (Қазақстан)
Банас Иозеф проф. (Польша)
Берсимбаев Р.И. проф., академик (Қазақстан)
Велесько С. проф. (Германия)
Велихов Е.П. проф., РҒА академигі (Ресей)
Кабульдинов З.Е. проф. (Қазақстан)
Қажыбек Е.З. проф., корр.-мүшесі (Қазақстан)
Қалимолдаев М.Н. проф., академик (Қазақстан), бас ред. орынбасары
Қамзабекұлы Д. проф., академик (Қазақстан)
Қойгелдиев М.К. проф., академик (Қазақстан)
Лупашку Ф. проф., корр.-мүшесі (Молдова)
Мохд Хасан Селамат проф. (Малайзия)
Новак Изабелла проф. (Польша)
Огарь Н.П. проф., корр.-мүшесі (Қазақстан)
Полещук О.Х. проф. (Ресей)
Поняев А.И. проф. (Ресей)
Сагиян А.С. проф., академик (Армения)
Таймагамбетов Ж.К. проф., академик (Қазақстан)
Хрипунов Г.С. проф. (Украина)
Шәукенова З.К. проф., корр.-мүшесі (Қазақстан)
Юлдашбаев Ю.А. проф., РҒА академигі (Ресей)
Якубова М.М. проф., академик (Тәжікстан)

«Қазақстан Республикасы Ұлттық ғылым академиясының Хабаршысы».

ISSN 2518-1467 (Online),

ISSN 1991-3494 (Print)

Меншіктенуші: «Қазақстан Республикасының Ұлттық ғылым академиясы»РҚБ (Алматы қ.).

Қазақстан Республикасының Ақпарат және коммуникациялар министрлігінің Ақпарат комитетінде 12.02.2018 ж. берілген № 16895-Ж мерзімдік басылым тіркеуіне қойылу туралы куәлік.

Тақырыптық бағыты: *іргелі ғылымдар саласындағы жаңа жетістіктер нәтижелерін жария ету.*

Мерзімділігі: жылына 6 рет.

Тиражы: 2000 дана.

Редакцияның мекенжайы: 050010, Алматы қ., Шевченко көш., 28, 219 бөл., 220, тел.: 272-13-19, 272-13-18,
<http://www.bulletin-science.kz/index.php/en/>

© Қазақстан Республикасының Ұлттық ғылым академиясы, 2020

Типографияның мекенжайы: «NurNaz GRACE», Алматы қ., Рысқұлов көш., 103.

Г л а в н ы й р е д а к т о р
д.х.н., проф. академик НАН РК
М.Ж. Журинов

Р е д а к ц и о н н а я к о л л е г и я:

Абиев Р.Ш. проф. (Россия)
Абылкасымова А.Е. проф., академик (Казахстан)
Аврамов К.В. проф. (Украина)
Апель Юрген проф. (Германия)
Баймуканов Д.А. проф., академик (Казахстан)
Баймуратов У.Б. проф., академик (Казахстан)
Байтанаев Б.А. проф., академик (Казахстан)
Байтулин И.О. проф., академик (Казахстан)
Банас Иозеф проф. (Польша)
Берсимбаев Р.И. проф., академик (Казахстан)
Велесько С. проф. (Германия)
Велихов Е.П. проф., академик РАН (Россия)
Кабульдинов З.Е. проф. (Казахстан)
Кажыбек Е.З. проф., чл.-корр. (Казахстан)
Калимолдаев М.Н. академик (Казахстан), зам. гл. ред.
Камзабекулы Д. проф., академик (Казахстан)
Койгельдиев М.К. проф., академик (Казахстан)
Лунашку Ф. проф., чл.-корр. (Молдова)
Мохд Хасан Селамат проф. (Малайзия)
Новак Изабелла проф. (Польша)
Огарь Н.П. проф., чл.-корр. (Казахстан)
Полещук О.Х. проф. (Россия)
Поняев А.И. проф. (Россия)
Сагьян А.С. проф., академик (Армения)
Таймагамбетов Ж.К. проф., академик (Казахстан)
Хрипунов Г.С. проф. (Украина)
Шаукенова З.К. проф., чл.-корр. (Казахстан)
Юлдашбаев Ю.А. проф., академик РАН (Россия)
Якубова М.М. проф., академик (Таджикистан)

«Вестник Национальной академии наук Республики Казахстан».

ISSN 2518-1467 (Online),

ISSN 1991-3494 (Print)

Собственник: РОО «Национальная академия наук Республики Казахстан» (г. Алматы).

Свидетельство о постановке на учет периодического печатного издания в Комитете информации Министерства информации и коммуникаций и Республики Казахстан № **16895-Ж**, выданное 12.02.2018 г.

Тематическая направленность: *публикация результатов новых достижений в области фундаментальных наук.*

Периодичность: 6 раз в год.

Тираж: 2000 экземпляров.

Адрес редакции: 050010, г. Алматы, ул. Шевченко, 28, ком. 219, 220, тел. 272-13-19, 272-13-18.

<http://www.bulletin-science.kz/index.php/en/>

© Национальная академия наук Республики Казахстан, 2020

Адрес типографии: «NurNazGRACE», г. Алматы, ул. Рыскулова, 103.

Editor in chief

doctor of chemistry, professor, academician of NAS RK

M.Zh. Zhurinov

Editorial board:

Abiyev R.Sh. prof. (Russia)
Abylkasymova A.E. prof., academician (Kazakhstan)
Avramov K.V. prof. (Ukraine)
Appel Jurgen, prof. (Germany)
Baimukanov D.A. prof., academician (Kazakhstan)
Baimuratov U.B. prof., academician (Kazakhstan)
Baitanaev B.A. prof., academician (Kazakhstan)
Baitullin I.O. prof., academician (Kazakhstan)
Joseph Banas, prof. (Poland)
Bersimbayev R.I. prof., academician (Kazakhstan)
Velesco S., prof. (Germany)
Velikhov Ye.P. prof., academician of RAS (Russia)
Kabuldinov Z.E. prof. (Kazakhstan)
Kazhybek E.Z. prof., corr. member. (Kazakhstan)
Kalimoldayev M.N. prof., academician (Kazakhstan), deputy editor in chief
Kamzabekuly D. prof., academician (Kazakhstan)
Koigeldiev M.K. prof., academician (Kazakhstan)
Lupashku F. prof., corr. member (Moldova)
Mohd Hassan Selamat, prof. (Malaysia)
Nowak Isabella, prof. (Poland)
Ogar N.P. prof., corr. member (Kazakhstan)
Poleshchuk O.Kh. prof. (Russia)
Ponyaev A.I. prof. (Russia)
Sagiyani A.S. prof., academician (Armenia)
Tajmagambetov Zh.K. prof., academician (Kazakhstan)
Khripunov G.S. prof. (Ukraine)
Shaukenova Z.K. prof., corr. member. (Kazakhstan)
Yuldashbayev Y.A., prof., academician of RAS (Russia)
Yakubova M.M. prof., academician (Tadjikistan)

Bulletin of the National Academy of Sciences of the Republic of Kazakhstan.

ISSN 2518-1467 (Online),

ISSN 1991-3494 (Print)

Owner: RPA "National Academy of Sciences of the Republic of Kazakhstan" (Almaty).

The certificate of registration of a periodical printed publication in the Committee of information of the Ministry of Information and Communications of the Republic of Kazakhstan No. **16895-Ж**, issued on 12.02.2018.

Thematic focus: *publication of the results of new achievements in the field of basic sciences.*

Periodicity: 6 times a year.

Circulation: 2000 copies.

Editorial address: 28, Shevchenko str., of. 219, 220, Almaty, 050010, tel. 272-13-19, 272-13-18,

<http://www.bulletin-science.kz/index.php/en/>

© National Academy of Sciences of the Republic of Kazakhstan, 2020

Address of printing house: «NurNaz GRACE», 103, Ryskulov str, Almaty.

**Zh. U. Myrkhalykov¹, S. G. Stepanov², R. T. Kaldybaev³,
A. E. Aripbaeva³, M. I. Satayev¹**

¹SILKWAY International University, Shymkent, Kazakhstan;

²Ivanovo State Polytechnic University, Ivanovo, Russia;

³South Kazakhstan State University, Shymkent, Kazakhstan.

E-mail: myrkhalykov@inbox.ru, step-sg@mail.ru, rashid_cotton@mail.ru,
akerke-1982@mail.ru, maratsatayev@mail.ru

ANALYSIS OF THE BASIC DIRECTIONS OF FIRE HOSES RUPTURE PRESSURES INCREASING

Abstract. The analysis of the main ways to increase the rupture pressure of these technical products was made based on the rupture pressures dependence in fire pressure hoses from the parameters of their woven reinforcing frame previously obtained by the authors. From a scientific and practical point of view, the main directions for increasing the bursting internal pressures in the FPH (Fire pressure hoses) are identified and analyzed. The developed methodology for calculating and designing of FPH is based on a relationship connecting internal hydraulic pressure *p-burst* with a breaking load *N-burst* in the weft thread and a number of other parameters.

To assess the influence of the parameters of the FPH woven reinforcing framework on the value of the internal bursting pressure, the latex FPH with a diameter of 77 mm manufactured by BEREG (Russia) made of polyester yarns and designed for a working pressure of 1.6 MPa, was chosen as the object of study.

The dependences of the bursting pressures values on the bursting strength of weft threads of FPH woven reinforcing frameworks, designed for a working pressure of 1.6 MPa, for various diameters of the arms cross sections are obtained. The influence of geometric densities on the basis and weft of the woven reinforcing frame on the value of internal burst pressure in the FPH is investigated.

When calculating the FPH strength under the action of internal hydraulic pressure, the effect on the value of the burst pressure in latex FPH manufactured by BEREG (Russia), designed for a working pressure of 1.6 MPa, such parameters as sleeve radius, geometric densities of base and weft was studied. When designing and creating new types of FPH, it is necessary to take into account the influence of these parameters on the burst pressure value.

Key words: pressure fire hose, reinforcing cage, polyester threads, internal rupture pressure.

Introduction. Fire pressure hoses (FPH) - one of the main means of extinguishing fires. Structurally, they are designed as flat-wound flexible piping systems on a fabric basis with rubber layers (layer) and serve to supply extinguishing liquid (water and aqueous foaming agents) under pressure at a distance to the fire site. In relation to the FPH, the requirement for their reliability and performance is extremely important, since the positive result in extinguishing fires directly depends on this, and as a result, the lives of people and property saved.

Due to the lack of its own enterprises for the production of FPH, the Republic of Kazakhstan purchases these products from foreign manufacturers.

The importance of purchases of FPH by Kazakhstan is explained not only by the fact that a significant part of the country belongs to the arid climate zone, but also by the fact that they become strategic in the event of emergencies associated with the occurrence of large fires in the country.

In order to reduce dependence on supplies of FPH from abroad, it is necessary to create our own production of new high-tech FPH in Kazakhstan. To achieve this goal, it is not enough just to have technology, production sites with equipment, and it is important to have our own scientific school in the field of theory, research, calculation and design of high-tech FPH. In this regard, in our opinion, it is of

considerable scientific and practical interest to analyze the main directions of increasing the strength characteristics of the FPH - their burst pressures.

An indispensable part of the device of any type of FPH is a woven reinforcing frame (WRF), fully absorbing the forces from the fluid pressure inside the fire hose, when it comes to non-rubberized FPHs, and to a decisive extent, in the case of rubberized, latexed and double-sided FPHs. Structurally, the frameworks of most of the FPH are seamless single-layer woven plain weave shells made on round looms. Along its circumference of the FPH are weft threads, mutually interwoven with warp threads located along the length of the FPH.

Most often, FPH WRF is made from polyester yarns based on polyethylene terephthalate (PET)

The calculation of the strength of the WRF is reduced mainly to the calculation of the strength of their reinforcing frames.

To date, on the basis of the nonlinear theory of calculating single-layer plain weave fabrics [1,2] we have developed the basic theoretical provisions [3-6], the calculation and design technique for commissioning [7,8], and a set of experimental studies has been carried out on the calculation of the strength of the FPH with hydraulic effects [3]. The developed methodology for calculating and designing FPH is based on the obtained dependence of the bursting internal hydraulic pressure a weft thread N_{rupt} and a number of other parameters of the reinforcing frame, having the form:

$$p\text{-burst} = \frac{2N\text{-burst} L_o}{R \left\{ L_u(2L_o - \beta_o d_o) + L_o \left[2(L_u^2 + (d_o \eta_{OB} + d_u \eta_{yB})^2)^{\frac{1}{2}} + \frac{0,212 L_y^2 (d_o \eta_{OB} + d_u \eta_{yB})^2}{(L_y^2 + (d_o \eta_{OB} + d_u \eta_{yB})^2)^{\frac{3}{2}}} - \beta_y d_u \right] \right\}}$$

where in R- radius fire hose; L_o , L_u - geometrical density respectively to FPH base and weft of reinforcing cage; d_o , d_y , η_{OB} , η_{yB} - respectively the diameters of the warp and weft reinforcing cage fire hose threads and the coefficients of the vertical buckling threads; β_o , β_y - coefficients characterizing the lengths of the zones of contact between the threads in WRF in fractions of the diameters of the warp and weft threads.

The rupture pressure characterizes the strength of the FPH, i.e., the ability of FPH WRF to resist rupture under the influence of internal hydraulic pressure. GOST R 51049-97 (Russia) [9] sets the values of bursting pressures for all types and diameters of the FPH. All FPHs manufactured at enterprises of the Russian Federation and operated in Kazakhstan must necessarily comply with this GOST for bursting pressures.

Let us analyze the main directions of increasing explosive internal pressures in the FPH. For this purpose, we take as an object of study latex FPH with a diameter of 77 mm produced by BEREG Production Association (Russia), made of polyester yarns based on polyethylene terephthalate (PET) and designed for a working pressure of 1.6 MPa.

An analysis of the dependence of the bursting internal pressures in the FPH on the parameters of their woven reinforcing cage, based on formula.

In this case, the initial parameters of the FPH WRF necessary for such a study were determined using the methods described in [3].

The structure of formula is such that the burst pressure of the fire hose is directly and inversely proportional to the bursting force of the weft threads and the radius of the FPH. With an increase (decrease) in the breaking strength of the weft threads, the breaking pressure in the FPH (that is, in fact, the strength of the fire hose) increases (falls) according to a linear law. The dependences of the burst pressures on the bursting forces of the FPH WRF weft threads, designed for a working pressure of 1.6 MPa, for various diameters of the cross sections of the arms are shown in figure 1.

From the analysis of the graphs it follows that with a decrease in the diameters of the FPH cross sections, the steepness of the characteristics increases.

In general, based on an analysis of formula, it be concluded that with a decrease (increase) in the radius of the fire hose, its rupture pressure increases (falls).

An increase in the breaking strength of weft threads FPH WRF is one of the directions for increasing the strength characteristics of FPH. This direction can be implemented in two possible ways.

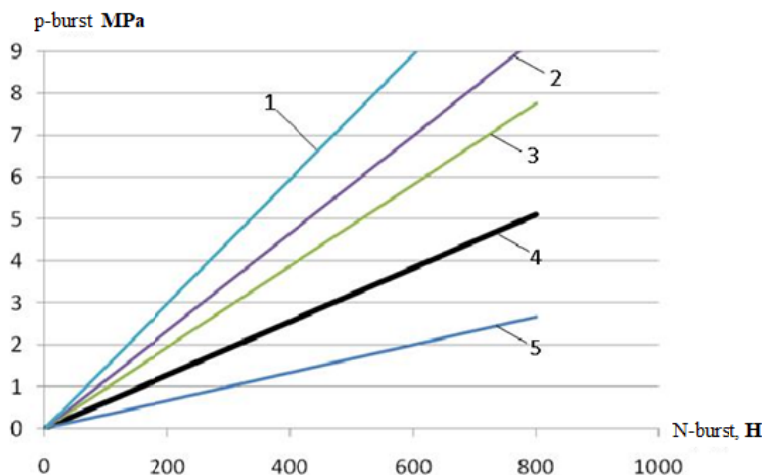


Figure 1 – The dependence of the rupture pressure p -burst on the breaking stress of the weft yarn of the FPH woven reinforcing frames at “BEREG” of different diameters: 1 - for the diameter of 51 mm; 2 - for the diameter of 66 mm; 3 - for the diameter of 77 mm; 4 - for the diameter of 89 mm; 5 - for the diameter of 150 mm

However, this path will lead to an increase in material consumption and weight of the FPH. The second method, in our opinion, is more acceptable, is that instead of traditional polyester threads, high-strength and wear-resistant threads, for example, ultra-high modulus (UHM) threads, or threads of ultra-high molecular weight polyethylene (UHMWPE) can be used as weft in the FPH was.

The first method consists in the fact that such weaving materials can be washed using such traditional materials for the production of such FPH WRF, such as, for example, polyester yarns.

But in this case, to increase the strength of the fire hose, it is necessary to use as weft threads of a larger diameter (greater linear density) and, accordingly, with a greater rupter strength. However, this path will lead to an increase in material consumption and weight of the FPH. The second method, in our opinion, is more acceptable, is that instead of traditional polyester threads, high-strength and wear-resistant threads, for example, ultra-high modulus (UHM) threads, or threads of ultra-high molecular weight polyethylene (UHMWPE) can be used as weft.

Based on formula, the influence of geometric densities on the base and weft of the woven reinforcing cage on the value of internal burst pressure studied (figure 2, 3).

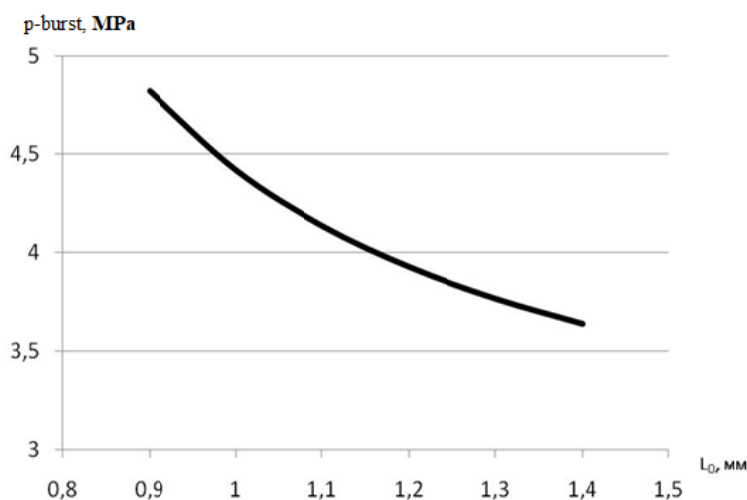


Figure 2 – The dependence of the rupture pressure p -burst from the geometric density on the basis of L_0 fabric of FPH latex reinforcing frame MG “Bereg” with diameter of 77 mm

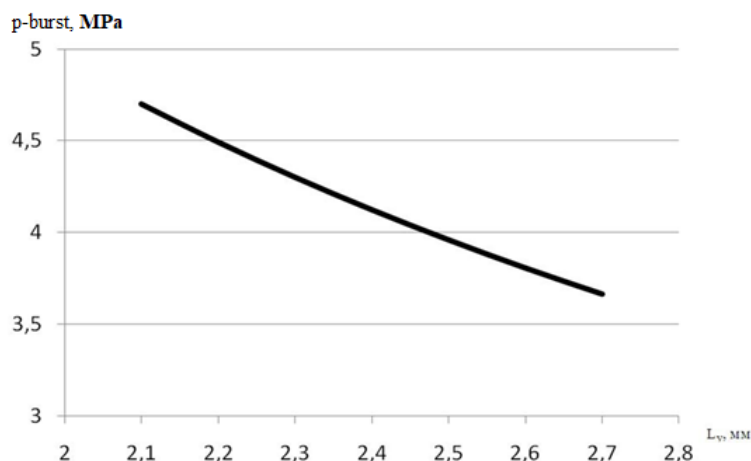


Figure 3 – The dependence of the burst pressure $p\text{-burst}$ from the geometric density of the weft L_w of the fabric of FPH Latex reinforcing frame MG "BEREG" with diameter of 77 mm

The analysis of the presented dependences shows that the burst pressure in the FPH substantially depends on the geometric densities of the base and weft of the reinforcing cage fabric. An increase (decrease) in the geometric densities of the fabric of such a FPH results in a decrease. It is important to consider the significant dependence of the bursting pressure on the bursting forces of weft threads, sleeve radii, geometric densities on the warp and weft of the fabric FPH WRF when designing new hoses. Reducing the geometric densities of the warp and weft of WRF threads (if there are technological capabilities for this), along with an increase in the breaking strength of the weft threads, seems the most effective way of increasing the strength characteristics of the FPH under hydraulic action.

Conclusion. On the basis of the obtained formula for calculating the FPH strength under the action of internal hydraulic pressure, the effect on the value of the rupture pressure in the latex FPH produced by Bereg Production Association (Russia), designed for a working pressure of 1.6 MPa, parameters such as the breaking stress threads, the radius of the sleeve and the geometric density at the base and weft.

The influence of these parameters on the value of the rupture pressure turned out to be the most significant, which must be taken into account when designing and creating new types of FPH.

Current study was carried out in the framework of the project AP05133582 "Development of methods for calculating and designing woven reinforcing frames for fire hoses with the aim of creating new high-tech samples of these technical products," funded by the Science Committee of the Ministry of Education and Science of the Republic of Kazakhstan.

Ж. У. Мырхалыков¹, С. Г. Степанов², А. Е. Арипбаева³,
Р. Т. Калдыбаев³, М. И. Сатаев¹

¹«SILKWAY» Халықаралық университеті, Шымкент, Қазақстан;

²Иваново мемлекеттік политехникалық университеті, Иваново, Ресей;

³М. Әуезов атындағы Оңтүстік Қазақстан мемлекеттік университеті, Шымкент, Қазақстан

ӨРТКЕ СУ СЕБЕТІН ТҮТІК ҚЫСЫМЫН АРТТЫРУДАҒЫ БАСТЫ БАҒЫТТАРДЫ ТАЛДАУ

Аннотация. Қысымды өртке су себетін түтік – тегіс иілгіш құбыр жолдары көбіктендіретін су және су ерітінділерін өрт ошағына қысым жасалған қашықтыққа жеткізу үшін қолданылады. Қысымды түтіктердің сенімділігі мен жұмыс қабілеттілігіне қойылатын талап өте маңызды, өйткені өртті сөндірудің оң нәтижесі оған тікелей байланысты. Өртке су себетін түтіктің маңызды параметрлерінің бірі – ішкі қысым әсерінен шлангтың жойылуға қарсы тұру қабілеттілігін сипаттайтын жарылатын ішкі қысым. Осыған байланысты гильзалардың жарылу қысымын жоғарылату жолдарын талдау маңызды. Өртке су себетін түтік құбырдағы үзілу қысымының олардың тоқылған армиленген қаңқа өлшемдеріне авторлар бұрын алынған тәуелділікке

сүйене отырып, осы техникалық бұйымның үзілу қысымын жоғарылатудың негізгі жолдарына талдау жүргізді. Өртке су себетін түтік құбырдың армиленіп тоқылған қаңқа өлшемдерінің ішкі үзілу қысымының шамасына әсерін бағалау үшін зерттеу объектісі ретінде ПО «БЕРЕГ» (Ресей) өндірісінің полиэфирлі жіптерден жасалған және 1,6 Мпа жұмыс қысымына есептелген диаметрі 77 мм латекстелген өртке су себетін түтік құбыр таңдап алынды. Жүргізілген зерттеулер үзілу қысымы кең дәрежеде арқау жібінің үзілу күшіне, су себу құбырының радиусына, армиленген қаңқа тоқымасының негіз және арқау бойынша геометриялық тығыздығына байланысты болып келетіндігін көрсетті. Арқау жіптерінің үзілу күші шамасының өсуі (төмендеуі) арқылы өртке су себетін түтік құбырының ажырау қысымы (яғни, су себетін түтігінің беріктігі) сызықтық заңы бойынша артады (төмендейді). Осылайша су себетін түтік құбыры көлденең қимасының төмендеуі негізінде құламалық сипаты өседі. Армиленген қаңқа тоқымасының негіз және арқау бойынша геометриялық тығыздығының өсуі (төмендеуі) өртке су себетін түтік құбырдың үзілу қысымының төмендеуіне (өсуіне) әкеледі. Ішкі үзілу қысымының арқау жіптерінің үзілу күшіне, түтікше құбырдың радиусына, армиленген қаңқа тоқымасының негіз бен арқау бойынша геометриялық тығыздығына аса тәуелді болатындығын жаңа өртке су себетін түтік құбырды жобалау кезінде есепке алған жөн.

Түйін сөздер: өртке су себетін түтікті құбыр, армиленген қаңқа, полиэфирлі жіптер, ішкі ажырау қысымы.

**Ж. У. Мырхалыков¹, С. Г. Степанов², А. Е. Арипбаева³,
Р. Т. Калдыбаев³, М. И. Сатаев¹**

¹Международный университет «SILKWAY», Шымкент, Казахстан;

²Ивановский государственный политехнический университет, Иваново, Россия;

³Южно-Казахстанский государственный университет им. М. Ауэзова, Шымкент, Казахстан

АНАЛИЗ ОСНОВНЫХ НАПРАВЛЕНИЙ ПОВЫШЕНИЯ РАЗРЫВНЫХ ДАВЛЕНИЙ НАПОРНЫХ ПОЖАРНЫХ РУКАВОВ

Аннотация. Напорные пожарные рукава – плоско сворачиваемые гибкие трубопроводы, применяемые для подачи воды и водных растворов пенообразователей на расстояние под давлением к очагу пожара. По отношению к напорным пожарным рукавам чрезвычайно важно требование к их надежности и работоспособности, так как от этого напрямую зависит положительный результат при тушении пожаров. Одним из важнейших параметров напорных пожарных рукавов является разрывное внутреннее давление, характеризующие прочность, т.е. способность рукава сопротивляться разрушению под действием внутреннего гидравлического давления. В связи с этим важно проанализировать пути повышения разрывных давлений рукавов. На основе ранее полученной авторами зависимости разрывных давлений в пожарных напорных рукавах от параметров их тканого армирующего каркаса выполнен анализ основных путей повышения разрывных давлений этих технических изделий. Для оценки влияния параметров тканого армирующего каркаса рукавов на величину внутреннего разрывного давления в качестве объекта исследования был выбран латексированный напорный пожарный рукав диаметром 77 мм производства ПО «БЕРЕГ» (Россия), изготовленный из полиэфирных нитей и рассчитанный на рабочее давление 1,6 МПа. Проведенное исследование показало, что в наибольшей степени разрывные давления зависят от разрывных усилий уточных нитей, радиусов рукавов, геометрических плотностей по основе и утку ткани армирующего каркаса. С увеличением (уменьшением) величины разрывного усилия уточных нитей разрывное давление в пожарных напорных рукавах (то есть фактически, прочность рукавов) возрастает (падает) по линейному закону. При этом с уменьшением диаметров поперечных сечений рукавов крутизна характеристик возрастает. Увеличение (уменьшение) геометрических плотностей по основе и утку ткани армирующего каркаса приводит к уменьшению (увеличению) разрывного давления пожарных напорных рукавов. Существенную зависимость внутреннего разрывного давления от разрывных усилий уточных нитей, радиусов рукавов, геометрических плотностей по основе и утку ткани армирующего каркаса важно учитывать при проектировании новых пожарных рукавов.

Ключевые слова: напорный пожарный рукав, армирующий каркас, полиэфирные нити, внутреннее разрывное давление.

Information about authors:

Myrkhalykov Zh., Academician of National Academy of Sciences of the Republic of Kazakhstan, Doctor of technical sciences, Professor, General Director of LLP “Research Institute of Innovation and Technological Modernization”, SILKWAY International University, Shymkent, Kazakhstan; myrkhalykov@inbox.ru; <https://orcid.org/0000-0002-4834-5089>

Stepanov S., Doctor of technical sciences, Professor of Department of Mechatronics and Radioelectronics, Ivanovo State Polytechnic University, Ivanovo, Russia; step-sg@mail.ru; <https://orcid.org/0000-0001-7648-832X>

Kaldybaev R., Candidate of technical sciences, Docent at the department of “Technology of manufactured and consumer goods of textile and light industry”, South Kazakhstan State University, Shymkent, Kazakhstan; rashid_cotton@mail.ru; <https://orcid.org/0000-0002-1370-7553>

Aripbaeva A. PhD, Senior lecturer at the department of “Technology and design of textile materials”, South Kazakhstan State University, Shymkent, Kazakhstan; akerke-1982@mail.ru; <https://orcid.org/0000-0003-1005-0856>

Satayev M., Corresponding member of National Academy of Sciences of the Republic of Kazakhstan, Doctor of technical sciences, Professor, Deputy Director of LLP “Research Institute of Innovation and Technological Modernization”, SILKWAY International University, Shymkent, Kazakhstan; maratsatayev@mail.ru; <https://orcid.org/0000-0001-9308-1839>

REFERENCES

[1] Myrkhalykov Zh.U., Satayev M.I., Stepanov S.G., Chistoborodov G.I. (2014) The theory of the formation and structure of the tissue on the basis of nonlinear mechanics of flexible filaments and its application to the solution of practical problems. Shymkent, Kazakhstan. ISBN: 978-9965-03-316-2 (in Russ.).

[2] Beysenbayev O.K., Ahmedov U.K., Issa A.B., Smaylov B.M., Esirkepova M.M., Artykova Zh.K. (2019) Receiving and research of the mechanism of capsulation of superphosphate and double superphosphate for giving of strength properties // News of the National Academy of Sciences of the Republic of Kazakhstan. Series of geology and technical sciences. Vol. 6, N 431 (2019). P. 36-45. ISSN 2518-170X (Online), ISSN 2224-5278 (Print). <https://doi.org/10.32014/2019.2518-170X.153>

[3] Stepanov S.G. (2007) The development of the theory of the formation and structure of the tissue on the basis of nonlinear mechanics of flexible filaments: dissertation for Doctoral degree in Technical Sciences: 05.19.02. Ivanovo State Textile Academy. Ivanovo, Russia (in Russ.).

[4] Aripbaeva A.E. (2018) Development of the theory, the development of methods of calculation and design of woven reinforcing carcasses firehoses: dissertation for Doctor of Philosophy (PhD): Almaty Technological University. Almaty, Kazakhstan (in Russ.).

[5] Aripbaeva A.E., Myrkhalykov Zh.U., Koifman O.I., Bazarov Y.M., Stepanov S.G. (2016) Promising direction in the field of calculation and design of reinforcing carcasses pressure firehoses on the basis of synthetic fibers [Perspektivnoe napravlenie v oblasti rascheta b proektirovaniya armiruyushih karkasov napornyh pozharnyh rukavov na osnove sinteticheskikh nitey] // Izvestiya VUZov. Tehnologiya textilnoy promyshlennosti. Vol. 59, Issue. 7. P 92-95 (in Russ.).

[6] Aripbaeva A.E., Stepanov S.G., Kaldybaev R.T. (2019) Dependence to calculate the bursting of the internal hydraulic pressure firehoses [Zavisimost dlya racheta razryvnogo vnutrennego gidraclicheskogo davleniya v pozharnyh napornyh rukavah] // Izvestiya VUZov. Tehnologiya textilnoy promyshlennosti. N 1. P. 186-191 (in Russ.).

[7] Aripbaeva A.E., Stepanov S.G., Kaldybaev R.T., Kaldybaeva G.Y., Mirzamuratova R.Sh. (2019) Evaluation of the accuracy of calculation according to the rupture of the internal hydraulic pressure firehoses [Ocenka tochnosti zavisimosti dlya racheta razryvnogo vnutrennego gidravlicheseskogo davleniya v pozharnyh napornyh rukavah] // Izvestiya VUZov. Tehnologiya textilnoy promyshlennosti. N 1. P. 191-195 (in Russ.).

[8] Aripbaeva A.E., Myrkhalykov Zh.U., Koifman O.I., Bazarov Y.M., Stepanov S.G. (2016) Method of calculation and rational design of reinforcing carcasses pressure firehoses on the basis of synthetic fibers [Metodika rascheta i racionalnogo proektirovaniya armiruyushih karkasov napornyh pozharnyh rukavov na osnove sinteticheskikh nitey] // Izvestiya VUZov. Tehnologiya textilnoy promyshlennosti. Vol. 59, Issue. 10. P. 83-87 (in Russ.).

[9] Aripbaeva A., Myrkhalykov Zh., Stepanov S. (2012) Method of design of reinforcing frames firehoses when subjected to internal hydraulic pressure // European Science and Technology. Materials of the XVII international research and practice conference. Munich, Germany. P. 42-50.

[10] State standard 51049-97. Firefighting equipment. Fire hoses. General technical requirements. Test methods. [GOST 51049-97. Tehnika pozharnaya. Rukava pozharnye napornye. Obshie tehniccheskie trebovaniya. Metody ispytaniya]. M., Russia, 1997 (in Russ.).

Publication Ethics and Publication Malpractice in the journals of the National Academy of Sciences of the Republic of Kazakhstan

For information on Ethics in publishing and Ethical guidelines for journal publication see <http://www.elsevier.com/publishingethics> and <http://www.elsevier.com/journal-authors/ethics>.

Submission of an article to the National Academy of Sciences of the Republic of Kazakhstan implies that the described work has not been published previously (except in the form of an abstract or as part of a published lecture or academic thesis or as an electronic preprint, see <http://www.elsevier.com/postingpolicy>), that it is not under consideration for publication elsewhere, that its publication is approved by all authors and tacitly or explicitly by the responsible authorities where the work was carried out, and that, if accepted, it will not be published elsewhere in the same form, in English or in any other language, including electronically without the written consent of the copyright-holder. In particular, translations into English of papers already published in another language are not accepted.

No other forms of scientific misconduct are allowed, such as plagiarism, falsification, fraudulent data, incorrect interpretation of other works, incorrect citations, etc. The National Academy of Sciences of the Republic of Kazakhstan follows the Code of Conduct of the Committee on Publication Ethics (COPE), and follows the COPE Flowcharts for Resolving Cases of Suspected Misconduct (http://publicationethics.org/files/u2/New_Code.pdf). To verify originality, your article may be checked by the Cross Check originality detection service <http://www.elsevier.com/editors/plagdetect>.

The authors are obliged to participate in peer review process and be ready to provide corrections, clarifications, retractions and apologies when needed. All authors of a paper should have significantly contributed to the research.

The reviewers should provide objective judgments and should point out relevant published works which are not yet cited. Reviewed articles should be treated confidentially. The reviewers will be chosen in such a way that there is no conflict of interests with respect to the research, the authors and/or the research funders.

The editors have complete responsibility and authority to reject or accept a paper, and they will only accept a paper when reasonably certain. They will preserve anonymity of reviewers and promote publication of corrections, clarifications, retractions and apologies when needed. The acceptance of a paper automatically implies the copyright transfer to the National Academy of Sciences of the Republic of Kazakhstan.

The Editorial Board of the National Academy of Sciences of the Republic of Kazakhstan will monitor and safeguard publishing ethics.

Правила оформления статьи для публикации в журнале смотреть на сайте:

www.nauka-nanrk.kz

ISSN 2518-1467 (Online), ISSN 1991-3494 (Print)

<http://www.bulletin-science.kz/index.php/en/>

Редакторы *М. С. Ахметова, Д. С. Аленов, А. Ахметова*
Верстка на компьютере *Д. А. Абдрахимовой*

Подписано в печать 14.10.2020.
Формат 60x881/8. Бумага офсетная. Печать – ризограф.
21 п.л. Тираж 500. Заказ 5.